

Advances in
Materials

Advances in Materials

Advances in Materials (AM) publishes reviews, full-length papers, and short communications recording original research results on, or techniques for studying the relationship between structure, properties, and uses of materials. The subjects are seen from international and interdisciplinary perspectives covering areas including metals, ceramics, glasses, polymers, electrical materials, composite materials, fibers, nanostructured materials, nanocomposites, and biological and biomedical materials. AM aims to be the leading source of primary communication for scientists investigating the structure and properties of all engineering materials.

<http://www.sciencepublishinggroup.com/j/am>

ISSN:2327-2503 (Print)

ISSN:2327-252X (Online)



Browse This Journal

→ About This Journal

→ Abstracting and Indexing

→ Editorial Board

→ Peer Reviewers

→ Archive

→ Guide for Authors

→ Article Processing Charges

→ Paper Submission

→ Journal Article Workflow

→ Publication Ethics

→ Copyright

→ FAQ

→ Launch a New Journal

→ Recommend to Library

Abstracting and Indexing

Advances in Materials has been included by the following Abstracting and Indexing databases:

WorldCat

WorldCat is the world's largest network of library content and services. WorldCat libraries are dedicated to providing access to their resources on the Web, where most people start their search for information.

CrossRef

CrossRef's general purpose is to promote the development and cooperative use of new and innovative technologies to speed and facilitate scholarly research. CrossRef's specific mandate is to be the citation linking backbone for all scholarly information in electronic form. CrossRef is a collaborative reference linking service that functions as a sort of digital switchboard. It holds no full text content, but rather effects linkages through CrossRef Digital Object Identifiers (CrossRef DOI), which are tagged to article metadata supplied by the participating publishers. The end result is an efficient, scalable linking system through which a researcher can click on a reference citation in a journal and access the cited article.

JournalSeek

Genamics JournalSeek is the largest completely categorized database of freely available journal information available on the internet. The database presently contains 100101 titles. Journal information includes the description (aims and scope), journal abbreviation, journal homepage link, subject category and ISSN. Searching this information allows the rapid identification of potential journals to publish your research in, as well as allow you to find new journals of interest to your field.

Chemical Abstract Services

CAS is the only organization in the world whose objective is to find, collect and organize all publicly disclosed substance information.

We build and maintain the world's largest collection of molecular substances, reactions, and related content that is vital to the work of researchers.

Electronic Journals Library

The Elektronische Zeitschriftenbibliothek EZB (Electronic Journals Library) offers an effective use of both scientific and academic journals publishing full text articles in the internet.

This service has been developed at the Universitätsbibliothek Regensburg (University Library of Regensburg) in cooperation with the Universitätsbibliothek der Technischen Universität München (University Library of the Technical University of Munich).

Zeitschriftendatenbank

The ZDB is the world's largest specialized database for serial titles (journals, annuals, newspapers etc., incl. e-journals). The ZDB-network is managed by the Staatsbibliothek zu Berlin; the database is held on a server of the Deutsche Nationalbibliothek.

The ZDB actually contains more than 1.6 million bibliographic records of serials from the 16th century onwards, from all countries, in all languages, held in 4.300 German and Austrian libraries, with 11.5 million holdings information. It does not contain contents, i. e. journal articles.

EZB

The Electronic Journals Library was founded in 1997 by the University Library of Regensburg in cooperation with the Technische Universität München University Library within the framework of a project. The aim of this project was to present e-journals to the library users in a clearly arranged user-interface and to create for the EZB member libraries an efficient administration tool for e-journal licences.

Academickeys

AcademicKeys.com is the premier source for academic employment. Academickeys' 17 discipline-focused sites offer comprehensive information about faculty, educational resources, research interests, and professional activities pertinent to institutions of higher education. More than 89% of the top 120 universities (as ranked by US News and World Report) are posting their available higher ed jobs with AcademicKeys.com.

Abstracting and Indexing



Alumina-based composites reinforced with silver particles

Enrique Rocha-Rangel^{1, *}, Elizabeth Refugio-García², José Miranda-Hernández³, Eduardo Terres-Rojas⁴

¹Universidad Politécnica de Victoria, 87138, México

²Departamento de Materiales, Universidad Autónoma Metropolitana, 02200, México

³Universidad Autónoma del Estado de México (UAEM-Valle de México), 54500, México

⁴Laboratorio de Microscopía Electrónica de Ultra Alta Resolución, IMP, 07730, México

Email address:

erochar@upv.edu.mx (E. Rocha-Rangel)

To cite this article:

Enrique Rocha-Rangel, Elizabeth Refugio-García, José Miranda-Hernández, Eduardo Terres-Rojas. Alumina-Based Composites Reinforced with Silver Particles. *Advances in Materials*. Vol. 2, No. 6, 2013, pp. 62-65. doi: 10.11648/j.am.20130206.11

Abstract: Al₂O₃/Ag composite ceramics were fabricated by the use of mechanical milling and pressureless sintering. Al₂O₃ + 10 wt.% Ag were mixed and milled during 12 h at 300 rpm in a horizontal mill, then with the powder mixture it was conformed cylindrical samples by uniaxial pressing using 300 MPa. The pressed samples were sintered during 1 h in an electrical furnace at 1300, 1400 and 1500°C respectively. Sinter was performed using an argon atmosphere inside the furnace in order to inhibit silver oxidation. XRD results established that silver retains its crystalline structure. On the other hand, density of samples is better with increments in temperature. However, the final relative density is small and about of 91%. Scanning electron microscopy observations show alumina's microstructure with very fine and homogeneous distributions of silver particles. Increments in sintering temperature are reflected as enhancements of the density and consequently of the fracture toughness of the Al₂O₃/Ag composite ceramics.

Keywords: Al₂O₃/Ag Composites, Fracture Toughness, Pressureless Sintering, Metallic Reinforcement

1. Introduction

Alumina (Al₂O₃) ceramic presents good mechanical properties such as: high hardness, high compressive strength, good chemical and thermal stability. However, its applications as structural material have been limited principally by its low fracture toughness. Al₂O₃ ceramics can be toughened with the incorporation of fine metallic particles [1], for this reason it has been prepared successfully some Al₂O₃-systems by different techniques such as: pressure-assisted thermal explosion [2], slip casting [3], metal infiltration [4-6], sintering high pressing [7], Chemical deposition [8], self-propagation high temperature synthesis [9] and reaction synthesized [10]. Nevertheless, most of these processes are costly and they are very complex in their procedures and control. From these studies authors have been documented that fracture toughness of a ceramic-metal composite can be controlled by the volume fraction of metallic phase as well as the size of metal particles and its homogeneous distribution in the ceramic matrix. With these

considerations in mind, simple and cheaper processes were developed for the production of ceramic-metal composites [11]. High-energy ball milling combined with pressureless sintering can be a substitute low-cost method for the production of ceramic-metal composite. The use of silver, that certainly is an expensive metal, is explained by the fact of the big ductility that possesses this metal, being this property an important consideration that several authors [12-16] have suggested as a characteristic significant than has to have a reinforced material of ceramics. For that, it has been proposed that one of the main reinforced mechanisms of ceramics by metals is the crack bridging due to ductile metallic ligaments. At this date, there is not knowing of studies over reinforced of ceramics by silver.

The aim of this study is to synthesize Al₂O₃-based composites reinforced with 10 wt.% silver using powder techniques in order to determine the effect of silver on the fracture toughness of the alumina-matrix.

2. Experimental

Starting materials were: Al₂O₃ powder (99.9 %, 1 μm, Sigma, USA) and silver powder (99.9 %, 1-2 μm, Aldrich, USA). Final silver content in the produced composites was 10 wt.%. Powder blends of 20 g were prepared in a ball mill with ZrO₂ media, the rotation speed of the mill was of 300 rpm, and studied milling time was 12 h. With the milled powder mixture, green cylindrical compacts 2 cm diameter and 0.2 cm thickness were fabricated by uniaxial pressing, using 300 MPa pressure. Then pressureless sinter in an electrical furnace was performed under 10 cm³/min argon flux, at three different temperatures (1300, 1400 and 1500 °C) during 1 h. The microstructure was observed by scanning electron microscopy (SEM) equipped with an analyzer by energy dispersive spectroscopy (EDS). Fracture toughness was estimated by the fracture indentation method [17], (in all cases twelve independent measurements per value were carrying out).

3. Results and Discussion

3.1. Density

Results of the density measurements in different samples are shown in Fig.1. As shown in this figure, is clear the tendency to density of the material, in the way that the sintered temperature is higher. This is because at higher temperatures the binding of the particles and the consequent closing of pores is provided by the migration of atoms due to the high activation energy reached at these temperatures. Shrinkage of different samples determined by direct measurements of the same before and after sintering was: 6, 12 and 19.34 % for sintered samples at 1300, 1400 y 1500°C respectively. What helps corroborate the reason because densification is increased at elevated temperatures.

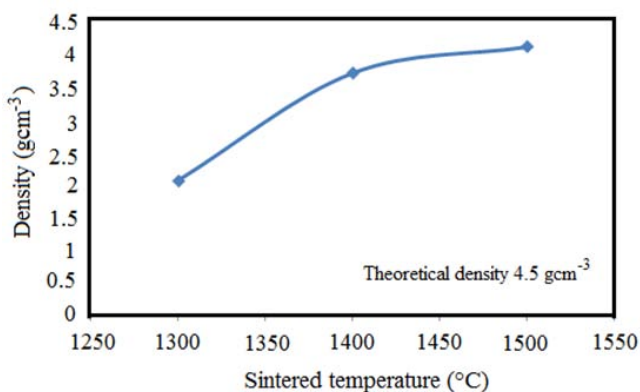


Figure 1. Sample's density as a function of sintered temperature.

3.2. X-Ray Diffraction

X-ray diffraction patterns of the powder mixture after grinding and sample sintered at 1500°C during 1 hour are shown in Fig. 2. In the corresponding spectrum to the mixture of powders, it is revealed the presence of the two

original components of the mixture; alumina and silver; in this same pattern it is not observed the presence of any diffraction peak that would designate the presence of any other compound which indicated contamination of the sample during the milling step. Regarding the pattern corresponding to the sample sintered, they have clearly defined the diffraction peaks of α-alumina phase and metallic silver. Comparing both diffraction patterns of fig. 2, is that the main diffraction peak of the silver that is the one located at 37.4° two theta degrees, slightly reduced in intensity after the sample was sintered, thinking allowing some oxidation of the silver. However, in the diffraction pattern of the sintered sample it is not showing any diffraction peak indicating the presence of a silver oxide, so it is discarded the oxidation of the silver during the sintered step.

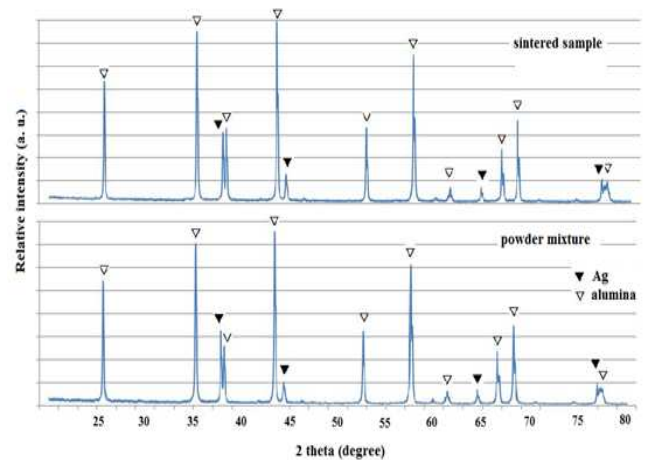


Figure 2. X-ray diffraction patterns of powders mixture after milling and sintered sample at 1500°C, during 1h.

3.3. Microstructure

Typical microstructures of the sintered samples at 1300, 1400 y 1500°C are presented in Fig. 3. As can be seen in these figures, is that with increments of the sintered temperature, samples tend to densify, because there is a decrease in the size and number of pores in these. This situation confirms the results of the density measurements made by the Archimedes method. Another important observation is that in all cases they have homogeneous microstructures, predominantly with equiaxed grains, but equally there are some deformed grains. The grain size increases in agreement with the increment of temperature. All these grains are spoken correspond to the ceramic phase of the composite material, it means is the alumina matrix. The silver particles are the very fine and bright dots observed in intergranular regions of the matrix. To confirm the presence of silver in these microstructures, energy dispersive spectroscopy (EDS) analyzes were performed on clear particles of the samples, A typical EDS spectrum is showing in fig. 3. In this spectrum it is observed that the principal component where the analyses were performed is silver.

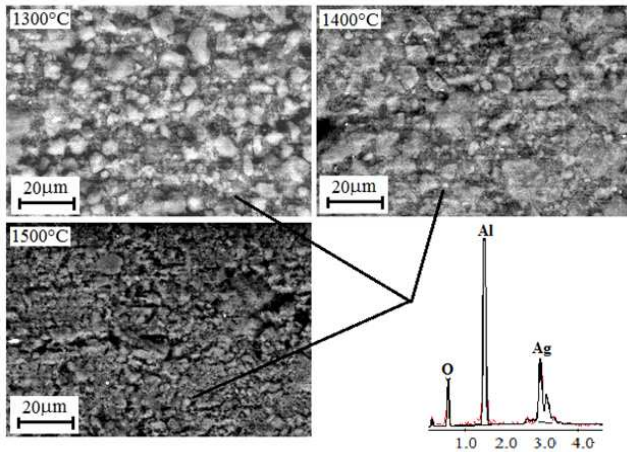


Figure 3. Microstructure of samples sintered at 1300, 1400 and 1500°C. Typical EDS spectrum of analysis performed in white dots of different samples.

3.4. Mechanical Properties

The results of the measurement of microhardness and fracture toughness performed in the samples sintered during 1 h at different temperatures are presented in Fig. 4. In both curves it is observed that mutually the microhardness and fracture toughness of alumina-silver composite are improved as the sintered temperature increases, this is a consequence of have a good densified body. The microhardness value reported in the literature [18] for pure alumina is 1175 HV, value significantly higher than that achieved by the compounds manufactured here, this difference is due to the lower degree of densification achieved in our composites. With respect to the fracture toughness the value reported in the literature for alumina is $3.2 \text{ MPa}\cdot\text{m}^{1/2}$ [13], while the value of this same property obtained by composites made here, has achieved in the best case $4.3 \text{ MPa}\cdot\text{m}^{1/2}$, equivalent value to a 34% higher. This improvement in fracture toughness is attributable to the incorporation into the ceramic matrix of a metal with high ductility such as silver. Several authors [1, 11, 13] have commented that the toughening mechanism in Al_2O_3 /metals composites is due to plastic deformation of the metallic phase, which forms crack-bridging ligaments. Thus it is illustrated the significant effect on the fracture toughness of alumina the incorporation therein of small amounts of a ductile metal as silver. However, it is important to consider that this improvement of the fracture toughness can be enhanced even if bodies can be manufactured with higher densifications. On the other hand, it would be interesting to conduct a study varying silver content in the matrix, as it is very likely get very different behaviors with other silver contents.

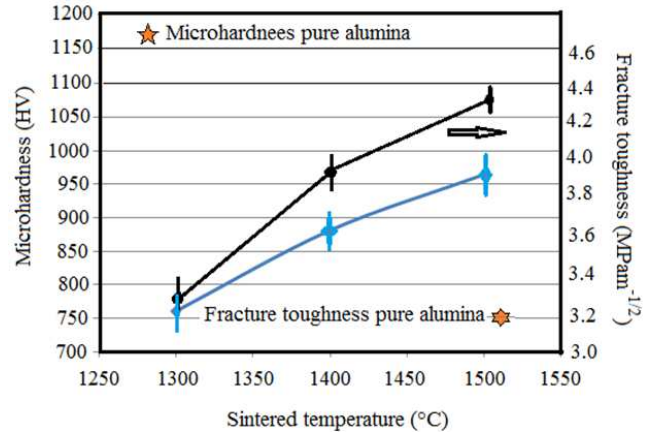


Figure 4. Microhardness and fracture toughness of samples sintered as a function of sintered temperature.

4. Conclusions

- ✓ Al_2O_3 -based composites can effectively be produced by inducing fine dispersions of silver particles, through a combination of experimental techniques, such as; mechanical milling and pressureless sintering (in an argon-atmosphere).
- ✓ The refined and homogeneous incorporation of silver in a ceramic matrix (Al_2O_3) improves its fracture toughness. Alternatively, increments in sintering temperature are reflected as enhancements of the density and consequently of the fracture toughness of the same one.
- ✓ From the fracture toughness measurements and microstructure observations, it can be commented that the toughening mechanism in Al_2O_3 /Ag composites is due to plastic deformation of the metallic phase, which forms crack-bridging ligaments.

Acknowledgements

The microscopy laboratory facility given by IMP and processing laboratories of UAM-A, UAEM and UPV is appreciated. In addition, ERR are grateful to CONACyT by the support given to carry out this work through Project 132406.

References

- [1] O.L. Ighodaro and O.I. Okoli, International Journal of Applied Ceramics Technology (2008)313-323.
- [2] N. Travitzkya, I. Gotmanb and N. Claussena, Materials Letters 57(2003)3422–3426.
- [3] M. Szafran, K. Konopka, E. Bobryk and K.J. Kurzydłowski, Journal of the European Ceramic Society 27(2007)651–654.
- [4] S. Avraham, P. Beyer, R. Janssen, N. Claussen and W.D. Kaplan, Journal of the European Ceramic Society 26(2006)2719–2726.

- [5] P. Agrawal and C.T. Sun, *Composites Science and Technology* 64(2004)1167–1178.
- [6] A. Matterna, B. Huchlerb, D. Staudeneckerb, R. Oberackera, A. Nagelb and M.J. Hoffmanna, *Journal of the European Ceramic Society* 24(2004)3399–3408.
- [7] K. Konopka, J.J. Bucki, S. Gierlotka, W. Zieliński, and K.J. Kurzyydowski, *Materials Characterization* 56(2006)394–398.
- [8] J. Li, J. Sun and L. Huang, *Materials Science and Engineering A* 323(2002)17–20.
- [9] D. Horvitz, I. Gotmana, E.Y. Gutmanasa and N. Claussen, *Journal of the European Ceramic Society* 22(2002)947–954.
- [10] A. Taotao, *Chinese Journal of Aeronautics* 21(2008)559-564.
- [11] E. Rocha-Rangel, E. Refugio-García, J. G. Miranda-Hernández and E. Terrés-Rojas, *Journal of Ceramic Processing Research*, 10[6](2009)744-747.
- [12] J. G. Miranda-Hernández, Master Thesis, Universidad Autónoma Metropolitana, Mexico (2006).
- [13] J. M. Miranda, S. Moreno, B. Soto and E. Rocha, *Journal of Ceramic Processing Research*, 7[4](2006)311-314.
- [14] V. Mercedes, Doctoral Thesis, Universidad Autónoma de Madrid, Instituto de Ciencia de Materiales de Madrid, Spain (2003).
- [15] A. Feder, I. Llanes and M. Anglada, *Bol. Soc. Esp. Ceram.* 43(2004)47-52.
- [16] R. Günther, T. Klassen, B. Dickau, F. Gärtner, A. Bartels and R. Bormann, *Journal of American Ceramic Society*, 84(2001)1509-1513
- [17] A.G. Evans and E.A. Charles, *Journal of the American Ceramic Society*, 59(1976)371-372.
- [18] J.F. Shackelford and R.H. Doremus, *Ceramic and Glass Materials: Structure, Properties and Processing*. Springer (2010).